

Formulation of Lubricant from Calabash Seed Oil

F. J. Owuna^{1*}, M. U. Dabai¹, M. A. Sokoto¹, U. Z. Faruq¹ and A. L. Abubakar²

¹*Department of Pure and Applied Chemistry, Usmanu Danfodiyo University, Sokoto, Nigeria.*

²*Department of Biochemistry, Usmanu Danfodiyo University, Sokoto, Nigeria.*

Authors' contributions

This work was carried out in collaboration between all authors. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/JERR/2018/v3i116866

Editor(s):

(1) Dr. Ahmed Bdour, Professor, Water Resources and Environmental Engineering, Department of Civil Engineering, The Hashemite University, Jordan.

Reviewers:

(1) Naima Khatir, University Center of Naama, Algeria.

(2) Imtiaz Ahmad, University of Peshawar, Pakistan.

(3) Hong Xu, Taiyuan University of Technology, China.

Complete Peer review History: <http://www.sciencedomain.org/review-history/27693>

Original Research Article

Received 17 September 2018

Accepted 25 November 2018

Published 08 December 2018

ABSTRACT

The engine oil market is faced with complex chemical reactions and difficult chemical engineering involved in the formulation of synthetic based engine oils, and therefore, the need to source for alternative base oils for engine oil formulation from vegetable oils has become urgent and inevitable. This research is aimed at formulation of lubricant using calabash seed oil (CSO). An experiment designed (Mixture Design Method using Minitab 17) was used to obtain the blend of CSO (28.75%), SN 500 (68.75%), and additive (2.50%) with improved physicochemical parameters. The lubricant obtained had kinematic viscosities 9.30 ± 2.11 cSt (at 100°C) and 53.11 ± 1.03 cSt (at 40°C), a viscosity index of 167 ± 0.51 , flash point of $240 \pm 2.01^\circ\text{C}$, and pour point of $-28 \pm 1.31^\circ\text{C}$. The lubricant obtained in this research had quality parameters that are comparable to those of synthesised environmentally acceptable engine oils, and are within the standard for engine oils.

Keywords: *Formulation; environment; lubricant; calabash seed oil.*

*Corresponding author: Email: jzr4do@gmail.com;

DEFINITIONS

ASTM = American Society for Testing and Materials

CSO = Calabash Seed Oil

FTIR = Fourier Transform Infra-Red Spectroscopy

GC-MS = Gas Chromatography Mass Spectroscopy

HTHS = High Temperature High Shear

mg/l = Milligram per Litre

mPa = Millipascal

SEA = Society of Automotive Engineers

Wt% = Weight Percent

1. INTRODUCTION

The engine oil market is faced with numerous challenge such as renewability of the base oils [1-3], availability and accessibility of the products [1,4,5], compatibility of the products with modern machines and equipment [6], and environmental acceptability of the products [1,2,7].

Leaders in the engine oil market have accepted the challenges and are formulating specialised products in conformity with the aforementioned challenge but the formulation processes are associated with costs because of the complex chemical reactions and difficult chemical engineering involved in the production of synthetic based engine oils [6].

The use of vegetable oils for the formulation of engine oil is associated with numerous advantages. Vegetable oils have high lubricity [2,4] owing to the polar group (esters) with long carbon chains [8,9], high viscosity indexes making them useful over a wide range of temperatures [2,10], they produce fewer emissions (due to higher boiling temperature range of esters) and have high volatilities and high flash points (because of their high molecular weight) [4,10] which makes them safe for transport and storage, and they are renewable, non-toxic, and ecofriendly [1,2,11].

The challenges inherent in the use of vegetable oils include poor low temperature stability [12] because of their high pour points (making them less applicable for any application at extreme cold temperatures), poor thermo-oxidative stability [2,4] owing to the degree of unsaturation of their molecular structures [7], relatively higher initial cost of production or processing [2,5] compared to mineral oils.

The use of vegetable oils for the production of environmentally acceptable engine oils is a promising development in addressing the drawbacks associated with the use of conventional mineral oils, the complex methods employed in the formulation of synthetic engine oils, and additionally, economic relevance in the local communities where vegetable oil crops are grown and processed [3-5,13-15].

This study is aimed at using calabash seed oil (CSO) for the formulation of lubricating engine oil.

2. METHODS

2.1 Sample Collection and Treatment

Calabash seeds (Appendix I) were obtained from Sokoto Metropolis, Sokoto State, North-western Nigeria, and authenticated by Botany Unit, Department of Biological Science, Faculty of Sciences, Usmanu Danfodiyo University, Sokoto. The seeds were dehulled, dried, ground into powder, and sieved to obtain a homogeneous powder. The powdered calabash seed (300.00 g) was weighed and preserved for oil extraction [7,16].

2.2 Oil Extraction

Soxhlet extractor (Fig. 1) was employed in the extraction of calabash seed oil (CSO) with n-hexane (6:1 w/w% of solvent/sample) as the extracting solvent (in 500 cm³ round-bottomed flask). The sample (50.00 g per each extraction) was placed in a thimble, while the n-hexane was heated gently (using a heating mantle). A reflux condenser was fitted (to cool the heated n-hexane), and the mixture was heated at 60°C for 5 hours, while the condensed hot-solvent soaked the thimble. The solvent siphoned into the flask when it reached the top of the siphon tube of the Soxhlet apparatus [5,7]. The oil was separated from the solvent with the aid of a rotary evaporator. The percentage yield of the CSO was calculated using equation 1:

$$\% \text{ Yield} = \text{Weight of Oil}(g) \times 100 / \text{Weight of the Sample}(g) \quad (1)$$

2.3 Lubricant Formulation

In order to achieve a better thermal and oxidative stability for the CSO [4,17], the CSO was blended with SN 500 mineral based oil and additive (poly alkylmethacrylate). A design of

experiment (Mixture Design method of Minitab 17) was used to obtain the best blend with improved quality parameters from the raw CSO extract. The blend of CSO, SN 500, and additive was done in a conical flask at a temperature of 45°C, and stirred at 600 rpm for 15 minutes, while a heating mantle equipped with a magnetic stirrer was used to achieve a homogeneous mixture [4,7].

2.4 Physicochemical Parameters of CSO and the Lubricant

The CSO extract and the formulated engine oil were analysed for their physicochemical properties as below (Appendix II):

2.4.1 Determination of kinematic viscosity

The oils were each poured into a viscometer tube and mounted upright in the viscometric bath which was maintained at 40 or 100°C. The oil in the tube was allowed to gain equilibrium for 15 minutes. When the equilibrium temperature was achieved, the oil level in the viscometer tube was adjusted using a suction pump to 7 mm above the upper mark of the viscometer tube. The time (t) taken for the oil to move from the upper mark to the lower mark of the viscometer tube was recorded [7]. The kinematic viscosity (KV) was obtained via equation 2:

$$KV (cSt) = C (cSt s^{-1}) \times t (s) \quad (2)$$

Where, **KV** is the kinematic viscosity; **C** is the calibration constant of the viscometer; **t** is the time.

2.4.2 Determination of viscosity index

Viscosity index (VI) of the oils were each obtained using values of kinematic viscosity obtained at 40 and 100°C with standard measurement table as determined by ASTM D-2270 method.

2.4.3 Determination of pour point

Pour point tester of accuracy of $\pm 3^\circ\text{C}$ was used to determine the pour points of the CSO and lubricating oil. The tester used methanol as the cooling solvent and has a minimum temperature of -68°C . The oil (45 cm³) was poured into a test jar to the levelled mark. Then the tester was cooled to -37°C . While cooling the tester, the oil jar was heated to 45°C with the aid of a water bath. The oil jar was cooled with another water bath to a temperature of 27°C. When the pour point tester had reached -36°C , the oil jar was placed in a horizontal position in the hole at the top of the tester and the pour point temperature was taken after 5 seconds when the oil showed no movement [4].

2.4.4 Determination of flash point

The flash point of the CSO and lubricating oil were each determined by heating a cup holding the oil and moving a flame over the oil at regular temperature, starting with a temperature of 28°C below the expected flash point of the oil. The bulb of the thermometer was immersed in the sample in order to allow monitoring and reading of the temperature at flash point. The flash occurred in the cup containing the CSO when the temperature of the oil had reached its flash point [7].



Fig. 1. A set up for the extraction of CSO

2.4.5 Determination of free fatty acid

The oil (2.00 g each of CSO and lubricating oil) was placed in a dry 250 cm³ -conical flask. 50 cm³ of ethanol and few drops (2-3) of phenolphthalein indicator were added. The mixture was heated at 60°C in a water bath for 10 minutes and then cooled. The mixture was titrated with 0.1 M KOH to the endpoint (with consistent shaking). A dark pink colour was observed and the volume of KOH used for the titration was recorded as the titre value [4]. The acid value and the free fatty acid value were calculated using equation 3 and 4:

$$\text{Acid value} \left(\frac{\text{mgKOH}}{\text{g sample}} \right) = \frac{\text{Volume KOH}(\text{cm}^3) \times \text{N KOH}(\text{mmol}/\text{cm}^3) \times 56.1 (\text{mg}/\text{mmol})}{\text{sample weight (g)}} \quad (3)$$

$$\text{Free Fatty Acid} \left(\frac{\text{mgKOH}}{\text{g sample}} \right) = 0.5 \times \text{Acid value} \quad (4)$$

Where, **KOH** is potassium hydroxide; **N** is the molar concentration of KOH; and **56.10** is the molecular weight of KOH.

3. RESULTS AND DISCUSSION

The formulated CSO lubricant with optimum physicochemical properties was obtained from the proportion with details as CSO (28.75% wt), SN 500 (68.75% wt), and additive (2.50% wt) (Table 1).

An index for evaluating the internal resistance in the motion of engine oil is kinematic viscosity [18]. The higher the fluid's viscosity, the thicker it will be and more energy will be needed to move an object through it [19]. Kinematic viscosities of the lubricant were found to be 53.11±1.03 cSt at 40°C and 9.30±2.11 cSt at 100°C (Table 2) which are lower compared to the values for synthesised oil (Appendix III) but are within the standard for engine oils [7]. Thus, the lubricant is useful for engine oil application.

The effect of changing temperatures on the kinematic viscosity of lubricating fluid is called viscosity index (VI) and it is inversely proportional to temperature: a higher change in viscosity in response to temperature variation indicates small viscosity index [18,20]. The viscosity index of the lubricant was found to be 167±0.51 (Table 2) which is comparable to the available commercial lubricating oil. This shows that the lubricant will experience less change in its viscosities as a result of variations in temperatures during applications.

The value of flash point of the lubricant was found to be 240±2.0°C (Table 2). Flash point is a useful lubricating oil property which suggests the minimum temperature at which the oil generates ignitable vapour [21], it determines lubricant's volatility and fire resistance [22]. The high flash point of the produced lubricant suggests a higher and complex nature of its molecular structure, and hence, has low risk associated with vapourisation during transport and storage.

However, the pour point of the lubricant was found to be -28±1.31°C (Table 2). According to Gobinda et al. [23], vegetable oil base stocks solidify at low temperatures making them less useful for some applications. Though the pour point of the lubricant is within the standard for engine oil [7], the produced lubricant would require a calculated amount of pour point depressant (PPD) for it to be applicable in extreme low temperature conditions as compared to synthesised engine oils. The PPDs will minimise the negative effects of precipitation at low temperatures during usage.

Free fatty acid component of crude vegetable oil is an important factor used to determine the food or oleochemical application of the vegetable oil; percentage free fatty acid greater than 5% suggests that the oil could be useful for the production of biodiesel, biolubricant, and bioplastics [24]. The free fatty acid value of the crude extract (1.06±12) decreases to 0.85±12 in the formulated lubricating oil (Table 2), this is due to the effect of additive in the formulated oil.

The result of the gas chromatography mass spectrum (GC-MS) of the extracted oil revealed the degree of unsaturation of the ester carbon atoms such as C₂₀H₃₆O₄, C₂₁H₃₈O₄, and C₂₃H₄₂O₄. The unsaturated nature of the oil extract is a factor that influence both the physical and chemical properties of the formulated lubricating oil [9,25,26]. Esters have been known for their lubricity and are good starting materials for the production of engine oils [26]. The presence of ester functionality was also confirmed by fourier transformed infra-red spectroscopy (FTIR) assay of the oil extract using sodium chloride plate [4] (Fig. 2). Alkene stretching vibration, =CH, for the oil extract was observed at 3011 cm⁻¹, which suggests that the oil extract has methylene interrupted double bond in its molecule [27,28]. Similarly, the carbonyl functional group was observed at 1744 cm⁻¹, which suggests the presence of ester in the oil extract since there is no visible O-H absorption band (Fig. 2).

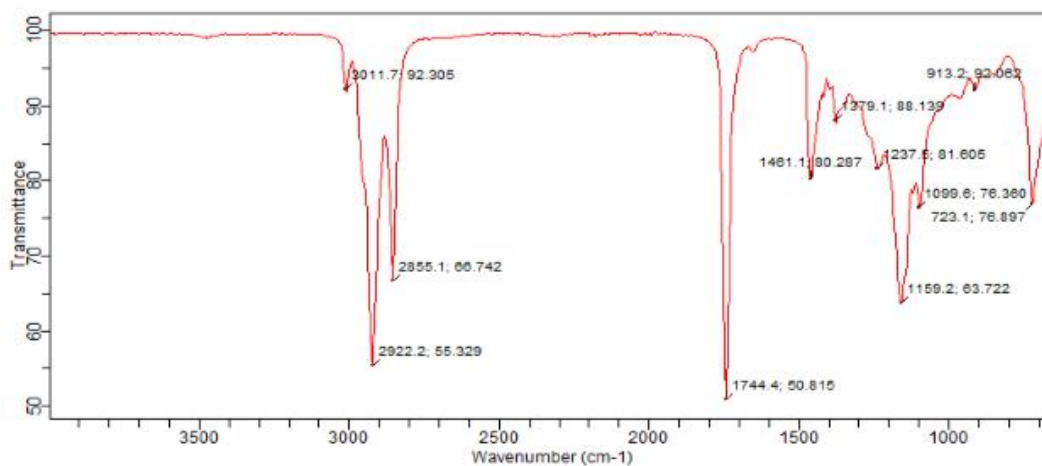


Fig. 2. FTIR spectrum for CSO extract

Table 1. Optimised blends for the lubricant formulation

Run order	CSO	SN 500	Additive	KV @ 100°C (cSt)	KV @ 40°C (cSt)	VI	FP (°C)	PP (°C)
1	0.00	90.00	10.00	9.00	89.20	75	233	-10
2	68.75	23.75	7.50	8.02	34.43	219	146	-13
3	23.75	68.75	7.50	10.50	50.18	207	241	-19
4	90.00	0.00	10.00	8.11	20.44	270	153	-24
5	28.75	68.75	2.50	9.31	53.00	166	238	-28
6	68.75	28.75	2.50	7.70	41.30	163	144	-16
7	10.00	90.00	0.00	10.70	65.20	157	236	-14
8	28.75	68.75	2.50	9.30	53.11	167	240	-28
9	90.00	0.00	10.00	8.11	20.62	268	153	-23
10	23.75	68.75	7.50	10.51	50.13	208	241	-18
11	90.00	10.00	0.00	8.60	44.90	172	166	-28
12	68.75	28.75	2.50	7.60	41.90	155	145	-15
13	68.75	23.75	7.50	8.02	34.47	217	145	-13
14	47.50	47.50	5.00	9.59	49.32	183	232	-29
15	0.00	90.00	10.00	9.50	89.17	85	231	-11
16	90.00	10.00	0.00	8.60	44.90	174	164	-27
17	47.50	47.50	5.00	9.50	49.32	182	233	-28
18	10.00	90.00	0.00	10.70	65.20	156	236	-14

Key: CSO = Calabash Seed Oil; KV = Kinematic Viscosity; VI = Viscosity Index; FP = Flash Point; PP = Pour Point

Table 2. Physicochemical properties of CSO and the lubricant

Parameters	Units	CSO	Lubricant	Engine oil range*
Kinematic Viscosity @ 40°C	cSt	21.78±1.22	53.11±1.03	> 28.80
Kinematic Viscosity @ 100°C	cSt	6.55±1.01	9.30±2.11	> 4.10
Viscosity Index		266±2.11	167±0.51	> 90.00
Flash Point	°C	145±1.01	240±2.01	> 150.00
Pour Point	°C	-11±0.01	-28±1.31	< -5.00
Free Fatty Acid	mg KOH g ⁻¹	1.06±12	0.85±12	-

Key: CSO = Calabash Seed Oil; (±) = Mean Value Plus or Minus Standard Deviation (n = 3); (*) = Owuna et al., 2018

4. CONCLUSION

This research was undertaken in order to formulate engine oil from calabash seed oil. The results obtained showed that a blend of CSO with mineral based oil and additive gave a formulation of lubricant that has parameters that are within the standard for engine oils and are comparable to commercially available engine oils. The chemical assay of the calabash seed extract revealed ester functionality which makes the oil good base oil for the formulation or synthesis of lubricating oil. The lubricant can be used as a substitute for any applications where synthesised engine oils are applicable if thermo-oxidative stability of the oil can be validated, and requisite (tailor-made) additive is incorporated in the formulation.

ACKNOWLEDGEMENTS

The authors wish to acknowledge Adeka E. Onyowo for the assistance on physicochemical analyses, and The Royal Family for the financial support.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

- Naima K, Liqid A. Waste oils as alternative fuel for diesel engine: A review. *Journal of Petroleum Technology and Alternative Fuels*. 2013;4:30-43.
- Ocholi O, Menkiti M, Auta M, Ezemagu I. Optimization of the operational parameters for the extractive synthesis of biolubricant from sesame seed oil via response surface methodology. *Egyptian Journal of Petroleum*. 2017;27:265-275.
- Jagadeesh KM, Satish VK, Venkatesh K, Kathyayini N. Environmentally friendly functional fluids from renewable and sustainable sources – A review. *Renewable and Sustainable Energy Reviews*. 2018;18:1787-1801.
- Dabai MU, Owuna FJ, Sokoto MA, Abubakar AL. Assessment of quality parameters of ecofriendly biolubricant from waste cooking palm oil. *Asian Journal of Applied Chemistry Research*. 2018;1:1-11.
- Muhammad C, Usman Z, Agada F. Biodiesel Production from *Ceiba pentandra* seed oil using CaO derived from snail shell as catalyst. *Petroleum Science and Engineering*. 2018;2:7-16.
- Mobarak HM, Niza ME, Masjuki HH, Kalam MA, Al Mahmud KAH, Habibullah M, Ashraful AM. The prospects of biolubricants as alternative in automotive applications. *Renewable and Sustainable Energy Reviews*. 2014;33:34-43.
- Owuna FJ, Dabai MU, Sokoto MA, Muhammad C, Abubakar AL. Use of *Lagenaria siceraria* seed oil for the production of environmentally friendly biolubricant. *American Journal of Applied and Industrial Chemistry*. 2018;2:1-7.
- Tirth M, Panchal AP, Chauhan DD, Merlin T, Jigar VP. A methodological review of bio-lubricants from vegetable oil based resources. *Renewable and Sustainable Energy Reviews*. 2017;70:65-70.
- Aloko S, Azubuike CP, Hebert ABC. Physicochemical properties and lubricant potentials of *Blighia sapida* Sapridaceaceae seed oil in solid dosage formulations. *Tropical Journal of Pharmaceutical Research*. 2017;16:305-311.
- Anjana S, Preeti S. Vegetable oils as lube bastocks: A review. *African Journal of Biotechnology*. 2013;12:880-891.
- Ozioko FU. Synthesis and study of properties of biolubricant based on *Moringa oleifera* oil for industrial application. *AU Journal of Technology*. 2017;17:137-142.
- Panchal T, Chauhan D, Thomas M, Patel J. Synthesis and characterization of biolubricants from tobacco seeds oil. *Research Journal of Agriculture and Environmental Management*. 2013;3:97-105.
- Abadi B, Shimels A. A review on potential and status of biofuel production in ethiopia. *Journal of Plant Sciences*. 2017;5:82-89.
- Adolf O, Akwasi A, Gyang NO, Amoa CA, Akorfa AA. Comparative assessment of some physico-chemical properties of seed oils of *Parkia biglobosa* and *Monodora myristica* with some commercial oils. *African Journal of Food Science*. 2018; 12:1-5.
- Anuchaya D, Vijay KD, Dhanapati D. Evaluation of the effectiveness of potato peel extract a natural antioxidant on biodiesel oxidation stability. *Industrial Crops & Products*. 2018;123:454-460.
- Mukhtar M, Muhammad C, Dabai MU, Muhammad M. Ethanolysis of calabash

- (*Langeneria sinceraria*) seed oil for the production of biodiesel. American Journal of Energy Engineering. 2014;2:141-145.
17. Jeevan TP, Jayaram SR. Experimental investigation on the performance of vegetable oil based cutting fluids in drilling AISI 304L using Taguchi technique. Tribology Online. 2018;13:50-56.
 18. Ratchadaporn I, Natthawud D, Churat T, Jutaporn C, Rameshpraba Ramaraj. An experimental investigation of palm oil as an environment friendly biolubricant. The 22nd Tri-U International Joint Seminar and Symposium, Jangsu University, China. October 18 - October 23, 2015;1-4.
 19. Jumat S, Bashar MA, Rahimi MY, Nadia S. Synthesis, reactivity and application studies for different biolubricants. Chemistry Central Journal. 2014;8:8-16.
 20. Ebtisam KH, Elmelawu MS, Salah AK, Elbasuny NM. Manufacture of environment friendly biolubricants from vegetable oils. Egyptian Journal of Petroleum. 2017;26: 53-59.
 21. Janes A, Chaineaux J. Experimental determination of flash points of flammable liquid aqueous solutions. Chemical Engineering Transactions. 2013;31:943-948.
 22. Ghazi T, Gunam RMFM, Idris A. Production of an improved biobased lubricant from *Jatropha curcas* as renewable source. Proceedings of the Third International Symposium on Energy from Biomass and Waste, Venice, Italy: CISA, Environmental Sanitary Engineering Centre. 2010;1-11.
 23. Gobinda K, Pranab G, Bragendra KS. Chemically modified vegetable oils to prepare green lubricants. Lubricants. 2017; 44:1-17.
 24. Japir AAW, Salmon S, Derawi D, Bahadi M, Al-Shuja'a S, Yusop M. Physicochemical characteristics of high free acid crude palm oil. Oilseeds & Fats Crops and Lipids. 2017;24:1-9.
 25. Ogunbusola EM, Fagbemi TN, Osundahunsi OI. Fatty acid characterisation, sterol composition and spectroscopic analysis of selected Cucurbitaceae seed oils. International Food Research Journal. 2017;24:696-702.
 26. Dhia FA, Sawsan AA. Fatty acids composition by GC-MS and most important physical chemicals parameters of seed oil pomogranate and grape seeds. Journal of Biology, Agriculture and Healthcare. 2016; 6:25-32.
 27. Aliyu AW, Richard UU, Ibrahim GW. Physico-chemical and GC-MS Analysis of Calabash (*Lagenaria siceraria*) seed oil. International Journal of Biochemistry Research & Review. 2016;14:1-7.
 28. Omahu OJ, Omale AC. Physicochemical properties and fatty acid composition of castor bean *Ricinus communis* L. seed oil. American Journal of Applied and Industrial Chemistry. 2017;3:1-4.

APPENDIX

Appendix I: Calabash Fruit (A) and Dehulled Seeds (B)



Appendix II: Analyses of Oils in Progress OVH Energies & Marketing, Kaduna, Nigeria



Appendix III: Fully Synthesised Mobil 1 5W-30 Oil (Mobil) Technical Data Sheet

Typical Properties

Mobil 1 5W-30	
SAE Grade	5W-30
Viscosity @ 100°C, cSt (ASTM D445)	11.0
Viscosity, @ 40°C, cSt (ASTM D445)	61.7
Viscosity Index	172
Sulfated Ash, wt% (ASTM D874)	0.8
HTHS Viscosity, mPa·s @ 150°C (ASTM D4683)	3.1
Pour Point, °C (ASTM D97)	-42
Flash Point, °C (ASTM D92)	230
Density @15.6 °C, mg/l (ASTM D4052)	0.855

Source: http://mobil.moovelub.com/sites/default/files/mobil_1_5w-30.pdf

© 2018 Owuna et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:
The peer review history for this paper can be accessed here:
<http://www.sciencedomain.org/review-history/27693>